

# TG-A6200 Reliability Testing

## 1. RA test

### Procedure

Tested for thermal resistance using a ASTM D5470 at different condition (room temperature, aging 125 °C, HAST and thermal shock).

**1.1 Room temperature @ 25°C**

**1.2 Thermal Aging @ 125°C (200 hrs, 400 hrs, 700 hrs, 1000 hrs)**

**1.3 Thermal HAST @ 85°C/85%RH (200 hrs, 400 hrs, 700 hrs, 1000 hrs)**

**1.4 Thermal Cycling @ -40°C to 120°C for 500 cycles (100 cycles, 200 cycles, 300 cycles, 400 cycles, 500 cycles)**

During testing and aging, the samples were maintained between two round aluminum disks of one square inch in surface area.

During Aging, clamps were used to hold a constant pressure on the sample.

## Results

| Code/(Unit : °C-in <sup>2</sup> /W) | 0 hr  | 200 hrs | 400 hrs | 700 hrs | 1000 hrs |
|-------------------------------------|-------|---------|---------|---------|----------|
| Room temperature                    | 0.290 | -       | -       | -       | -        |
| Thermal Aging                       | 0.290 | 0.288   | 0.289   | 0.290   | 0.291    |
| Thermal HAST                        | 0.290 | 0.291   | 0.292   | 0.289   | 0.292    |

| Code/(Unit : °C-in <sup>2</sup> /W) | 100 cycles | 200 cycles | 300 cycles | 400 cycles | 500 cycles |
|-------------------------------------|------------|------------|------------|------------|------------|
| Thermal Cycling                     | 0.288      | 0.290      | 0.292      | 0.291      | 0.289      |


**Test method: ASTM D5470**

**Heat power: 30W**

**Pressure: 30 psi**

**Specimen thickness: 1.0mm**

**Specimen Area: 1 inch<sup>2</sup>**

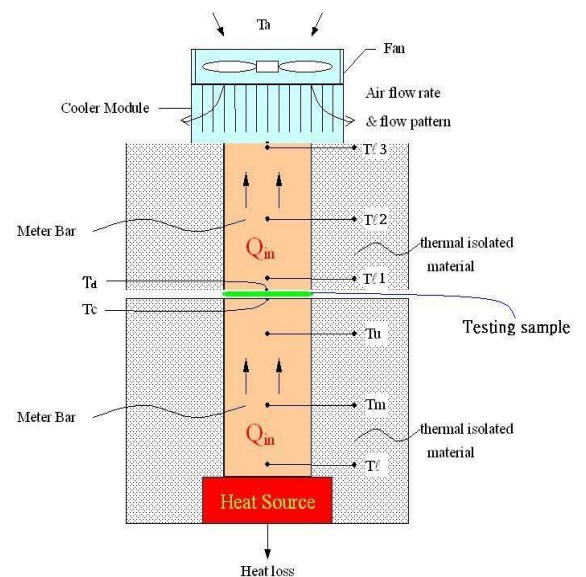

**T-Global Technology Co., Ltd**

No. 33, Ln. 50, Daren Rd., Taoyuan City, Taoyuan County 33068, Taiwan

TEL: +886-3-3618899

FAX: +886-3-3665666

[www.tglobalthermal.com](http://www.tglobalthermal.com)

[www.tglobal.com.tw](http://www.tglobal.com.tw)



# TG-A6200 Reliability Testing

## 2. Breakdown Voltage Test

### Procedure

Tested for Breakdown Voltage Test using a ASTM D149 at different condition (room temperature, aging 125°C, HAST and thermal shock).

**3.1 Room temperature @ 25°C**

**3.2 Thermal Aging @ 125°C (200 hrs, 400 hrs, 700 hrs, 1000 hrs)**


**3.3 Thermal HAST @ 85°C/85%RH (200 hrs, 400 hrs, 700 hrs, 1000 hrs)**

**3.4 Thermal Cycling @ -40°C to 120°C for 500 cycles (100 cycles, 200 cycles, 300 cycles, 400 cycles, 500 cycles)**

## Results

| High pot (AC @ kV) | 0 hr | 200 hrs | 400 hrs | 700 hrs | 1000 hrs | 2000 hrs |
|--------------------|------|---------|---------|---------|----------|----------|
| Room temperature   | >6   | -       | -       | -       | -        | -        |
| Thermal Aging      | >6   | >6      | >6      | >6      | >6       | >6       |
| Thermal HAST       | >6   | >6      | >6      | >6      | >6       | >6       |

| High pot (AC @ kV) | 100 cycles | 200 cycles | 300 cycles | 400 cycles | 500 cycles |
|--------------------|------------|------------|------------|------------|------------|
| Thermal Cycling    | >6         | >6         | >6         | >6         | >6         |

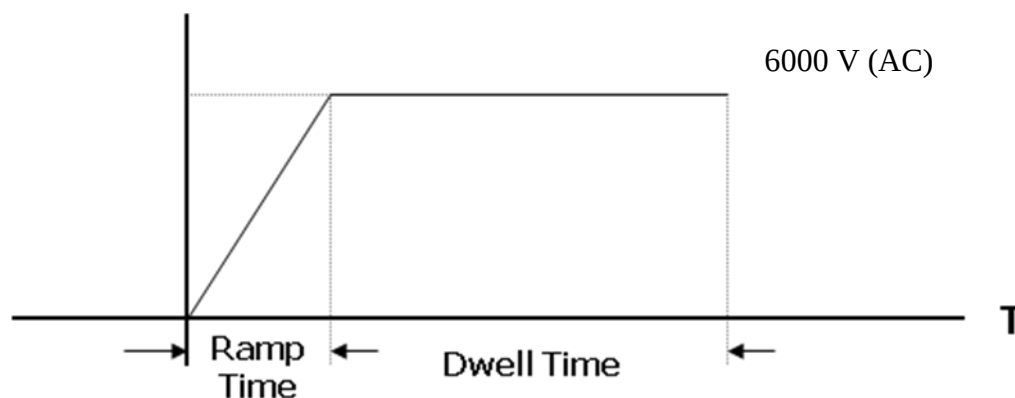

Ramp time: 20 sec

Dwell time: 60 sec

Max Voltage: 6000 V (AC)

### Note:

The data is for design engineer guidance only. Observed performance varies in application. Engineers are reminded to test the material in applications.

T-Global Technology Co., Ltd

No. 33, Ln. 50, Daren Rd., Taoyuan City, Taoyuan County 33068, Taiwan

TEL: +886-3-3618899

FAX: +886-3-3665666

[www.tglobalthermal.com](http://www.tglobalthermal.com)

[www.tglobal.com.tw](http://www.tglobal.com.tw)

